arXiv:cond-mat/0505535v1 [cond-mat.mes-hall] 21 May 2005

Theory of Spin Hall conductivity in n-doped GaAs

Hans-Andreas Engel, Bertrand I. Halperin, Emmanuel I. Rashba
Department of Physics, Harvard University, Cambridge, Massachusetts 02138

We develop a theory of extrinsic spin currents in semiconductors, resulting from spin-orbit coupling at charged scatterers, which leads to skew scattering and side jump contributions to the spin Hall conductance. Applying the theory to bulk n-GaAs, without any free parameters, we find spin currents that are in reasonable agreement with recent experiments by Kato *et al.* [Science **306,** 1910 (2004)].

Generating and manipulating non-equilibrium spin magnetization by electric fields is one of the most desirable goals of semiconductor spintronics, because electric fields have potentialities for accessing individual spins at nanometer scale. Spin-orbit (SO) coupling is a mechanism for achieving this goal. It has the prominent consequence of the spin-Hall effect (SHE), where an electric-current can induce a transverse spin current and a non-equilibrium spin accumulation near sample boundaries. Recent observations of this effect are important experimental achievements [1, 2]. Theoretically, two different mechanisms of SHE were proposed. The *extrinsic* mechanism [3, 4, 5] is based on spin-dependent scattering of electrons by impurities and is mostly due to Mott skew scattering [6]. An *intrinsic* mechanism has also been proposed, which is related to the concept of dissipationless spin currents in a perfect crystal [7, 8].

The theory of spin transport in media with SO coupling is rather intricate and includes all problems inherent in the theory of anomalous Hall effect (AHE), which has a long history; for reviews see [9, 10]. Also, the precise definition of spin currents is still under dispute because of the problems stemming from spin nonconservation in media with SO coupling. If spin-relaxation rates are small, a spin current with non-zero divergence can lead to spin accumulations, which are experimentally observable quantities [11, 12, 13]. However, because spin-currents are even with respect to time inversion, they do not necessarily vanish in thermodynamic equilibrium, hence their relation to spin transport and spin accumulation is far from obvious [14].

These problems inherent in the spin-transport theory make identification of physical mechanisms underlying the SHE observed in Refs. 1 and 2 rather challenging. On the one hand, Wunderlich *et al.* [2] observed a strong SHE in two-dimensional (2D) layers of p-GaAs and ascribed it to the *intrinsic* effect because of the large magnitude of the effect and large splitting of the energy spectrum typical of heavy holes. On the other hand, Kato *et al.* [1] attribute their measurement of SHE in three-dimensional n-GaAs layers (2μm thick) to the *extrinsic* mechanism. We believe that this is indeed the case as we explain in this work. Although an intrinsic spin Hall effect, driven by the k^3-Dresselhaus SO coupling [15], could give rise to spin accumulation in this system, as proposed in Ref. 16, its estimated size, when impurity scattering is taken into account, is an order of magnitude smaller than the observations. Further, because of the large sample thickness, a specifically 2D mechanism of spin accumulation proposed recently be Usaj and Balseiro [17] and Nikolić *et al.* [18] and relying on the properties of near-edge states cannot play a role in the geometry of Ref. 1.

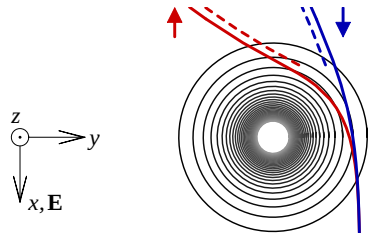

Figure 1: Spin-dependent scattering at an attractive impurity. We show the classical trajectories (solid lines), for a screened Coulomb potential and for strongly exaggerated spin-orbit coupling with $\lambda > 0$ and with quantization axis $\hat{\mathbf{z}}$. The skew-scattering current results from different scattering angles for spin-$\uparrow$ and spin-$\downarrow$ and leads to a positive spin Hall conductivity, $\sigma_{\rm SS}^{\rm SH} = -j^z_{{\rm SS},y}/E_x > 0$. Further, we show the horizontal displacement due to the side jump effect (dashed lines), contributing to the spin current with opposite sign.

In the following, we develop a theory of extrinsic spin currents in a 3D electron system. It results from intrinsic SO coupling in the bulk crystal that produces a SO contribution to the impurity potential. (This effect can occur even when the host crystal is inversion symmetric, so that spin is conserved outside the radii of the impurity potentials.) We find that impurity scattering and SO interaction in n-GaAs are strong enough to support spin-currents that are in reasonably good agreement with findings by Kato *et al.* [1] without using any adjustable parameters. Although the sign of our result is opposite to that mentioned in Ref. 1, there remains some uncertainty about the absolute sign in the experiments [19]. Since our result contains two contributions of opposite sign, and we have employed several approximations, we would believe the extrinsic mechanism to be relevant even if it turns out that the difference in the sign of the effect persists.

We consider an electron Hamiltonian of form

$$H = \frac{\hbar^2 k^2}{2m^*} + V(\mathbf{r}) + \lambda\, \boldsymbol{\sigma} \cdot (\mathbf{k} \times \nabla V)\,, \qquad (1)$$

where $V(\mathbf{r})$ is an electron potential energy that varies

slowly on the scale of the host lattice constant. In vacuum, the last term of Eq. (1) results from relativistic corrections in the Pauli equation and is known as Thomas term, with $\lambda = -\hbar^2/4m_0^2c^2 \approx -3.7\times10^{-6}$ Å^2, vacuum electron mass m_0, and velocity of light c. In direct gap cubic semiconductors like GaAs, a SO interaction of the same form develops in the framework of the $\mathbf{k}\cdot\mathbf{p}$ model due to the coupling of a s-type conductance band to p-type valence bands. This coupling is well established and, for asymmetric 2D systems, it leads to the Rashba term. For conduction band electrons in the 8×8 Kane model, one finds $\lambda = \left(P^2/3\right)\left[1/E_0^2 - 1/\left(E_0+\Delta_0\right)^2\right]$ in third-order perturbation theory, with gap E_0, SO splitting Δ_0 between the $J=\frac{3}{2}$ and $J=\frac{1}{2}$ hole bands, and a properly normalized interband matrix element P of the momentum [20]. All these parameters are large (i.e., of atomic scale) since they result from the strong crystal potential. For example, for GaAs one finds $\lambda = 5.3$ Å^2. Thus, the SO coupling in n-GaAs is by six orders of magnitude stronger than in vacuum and has the *opposite sign*. This enhancement of SO coupling is critical for developing large extrinsic spin currents.

In the 3D problem that we consider, SO coupling comes only through the potential energy $V(\mathbf{r})$ of Eq. (1), that can be either electron energy in an impurity center or its energy $-e(\mathbf{E}\cdot\mathbf{r})$ in a driving electric field, where e is the charge of an electron, i.e., $e<0$. We ignore here the SO k^3 (Dresselhaus) correction to the electron energy in pure GaAs, which is small and is absent in the 8×8 Kane model.

We now analyze the effect of the SO coupling in Eq. (1) on the scattering at impurities, which leads to the extrinsic spin Hall effect. This comprises two contributions, one resulting from the skew-scattering at the impurities [6] and the other from the shift of the scattered wave packet [21] (known as side jump contribution). These contributions are shown schematically in Fig. 1.

The skew scattering contribution is calculated in the lowest order both in SO interaction and in $1/k_{\rm F}\ell$, with Fermi momentum k_F and mean free path ℓ. To this end, we describe the system by a spin-dependent Boltzmann equation and a distribution function written as a 2×2 spin matrix $\hat{f} = [f_0(\mathbf{k}) + \phi(\mathbf{k})]\,\mathbb{1} + \mathbf{f}(\mathbf{k})\cdot\boldsymbol{\sigma}$, with equilibrium distribution function f_0. In the following, we suppress the identity matrix $\mathbb{1}$. The collision integral on the right hand side of the Boltzmann equation has the form

$$-\left(\frac{\partial\hat{f}(\mathbf{k})}{\partial t}\right)_{\rm coll} = n_i \sum_{\mathbf{k}';\ k'=k} \frac{\hbar k}{m^*}\frac{\overleftrightarrow{d\sigma}}{d\Omega}\left[\hat{f}(\mathbf{k}) - \hat{f}(\mathbf{k}')\right], \tag{2}$$

where n_i is the impurity density. The scattering cross section $\overleftrightarrow{d\sigma}/d\Omega$ is spin-dependent and mixes spin components of the incoming flux. In the general case, this spin dependence is rather complex [22]. However, it simplifies essentially when we expand Eq. (2) in SO coupling and neglect the cross terms containing spin-dependent contributions of both $\overleftrightarrow{d\sigma}/d\Omega$ and $\hat{f}$. For a central symmetric impurity potential, we can then write

$$\frac{\overleftrightarrow{d\sigma}}{d\Omega}\left[\hat{f}(\mathbf{k}) - \hat{f}(\mathbf{k}')\right] = I(\vartheta)\left[\hat{f}(\mathbf{k}) - \hat{f}(\mathbf{k}')\right] + I(\vartheta)S(\vartheta)\boldsymbol{\sigma}\cdot\mathbf{n}\left[\phi(\mathbf{k}) - \phi(\mathbf{k}')\right], \tag{3}$$

where $\vartheta = \vartheta_{\mathbf{k}\mathbf{k}'}$ is the angle between $\mathbf{k}'$ and $\mathbf{k}$, and $\mathbf{n} = \mathbf{k}'\times\mathbf{k}/|\mathbf{k}'\times\mathbf{k}|$ is the unit vector normal to the scattering plane. The coefficient $I(\vartheta)$ is the spin-independent part of the scattering cross section, while $S(\vartheta)$ is the so-called Sherman function [6, 22, 23], which measures the polarization of outgoing particles scattered into direction $\mathbf{k}$ from an unpolarized incoming beam of momentum $\mathbf{k}'$.

To lowest order in the electric field, the left hand side of the Boltzmann equation equals $e\mathbf{E}\cdot\frac{\partial f_0}{\partial\mathbf{p}} = (e\hbar/m^*)(\mathbf{E}\cdot\mathbf{k})\frac{\partial f_0}{\partial\varepsilon}$, where the isotropy of $f_0(\mathbf{k})$ was used. The Boltzmann equation may then be solved with the following ansatz. First, the usual spin-independent term is set to $\phi(\mathbf{k}) = \mathbf{k}\cdot\mathbf{E}\,C_k$ [typically, $C_k = -(e\hbar\tau/m^*)\frac{\partial f_0}{\partial\varepsilon}$ with transport lifetime τ]. Second, we use $\mathbf{f}(\mathbf{k}) = (\mathbf{E}\times\mathbf{k})\,D_k$ for the spin polarization due to SO interaction. This structure is motivated by the physics of Mott scattering, namely, that the spin polarization is perpendicular to the scattering plane defined by incoming electrons that drift in the direction of $-\mathbf{E}$ and are scattered into $\mathbf{k}$. Here, C_k and D_k are spherically symmetric functions of $\mathbf{k}$.

With this ansatz, we can evaluate the collision integrals on the right hand side of the Boltzmann equation. Integrating over the direction of $\mathbf{k}'$, $d\Omega\,(\mathbf{k}') = d\varphi\,d\vartheta\sin\vartheta$, where φ is the the azimuth of $\mathbf{k}'$ in the plane perpendicular to $\mathbf{k}$, and suppressing an overall factor of $n_i\hbar k/m^*$ in Eq. (2), we obtain (see App. A)

$$\begin{aligned}&\int d\Omega(\mathbf{k}')\,I(\vartheta)\,(\mathbf{k}-\mathbf{k}')\cdot(\mathbf{E}\,C_k + \boldsymbol{\sigma}\times\mathbf{E}\,D_k)\\ &= \left[\mathbf{k}\cdot\mathbf{E}\,C_k + \mathbf{k}\cdot(\boldsymbol{\sigma}\times\mathbf{E})D_k\right]\int d\Omega\,I(\vartheta)\,(1-\cos\vartheta),\end{aligned} \tag{4}$$

where the integral on the right is proportional to the inverse transport time τ^{-1}, and

$$\begin{aligned}&\int d\Omega(\mathbf{k}')\,I(\vartheta)\,S(\vartheta)\,(\boldsymbol{\sigma}\cdot\mathbf{n})\,(\mathbf{k}\cdot\mathbf{E} - \mathbf{k}'\cdot\mathbf{E})\,C_k\\ &= -\frac{1}{2}\,\mathbf{k}\cdot(\boldsymbol{\sigma}\times\mathbf{E})\,C_k\int d\Omega\,I(\vartheta)\,S(\vartheta)\sin\vartheta.\end{aligned} \tag{5}$$

Since the left hand side of the Boltzmann equation only depends on the component of $\mathbf{k}$ along the electrical field, this must also be the case on the right hand side. Thus, the second term in Eq. (4) must cancel with Eq. (5), determining $D_k = \frac{1}{2}\gamma_k C_k$. We defined the transport skewness

$$\gamma_k = \frac{\int d\Omega\,I(\vartheta)\,S(\vartheta)\sin\vartheta}{\int d\Omega\,I(\vartheta)\,(1-\cos\vartheta)}, \tag{6}$$

which describes the effect of skew-scattering on the distribution function and depends on the structure of the

scattering center and on the energy of the scattered particle. Therefore, our ansatz is self-consistent, and the solution of the Boltzmann equation is

$$\hat{f}(\mathbf{k}) = f_0(k) + \mathbf{k}\cdot\left[\mathbf{E} + \frac{\gamma_k}{2}\left(\boldsymbol{\sigma}\times\mathbf{E}\right)\right] C_k, \qquad (7)$$

i.e., the components of $\mathbf{f}(\mathbf{k})$ are $f_\mu(\mathbf{k}) = \frac{\gamma_k}{2}\left(\mathbf{E}\times\mathbf{k}\right)_\mu C_k$.

Now we calculate the contribution of skew-scattering to the spin current, $\mathbf{j}^\mu_{\rm SS} = n\,\langle\sigma_\mu\,\mathbf{v}_0\rangle$, with density n and with $\mathbf{v}_0 = \hbar\mathbf{k}/m^*$ (SO contributions to the velocity are analyzed below). We obtain

$$j^\mu_{{\rm SS},\,\kappa} = \mathrm{Tr}\,\sigma_\mu \int \frac{d^3k}{(2\pi)^3}\,\frac{\hbar\,k_\kappa}{m^*}\,\hat{f}(\mathbf{k}) = \frac{\gamma}{2e}\,\varepsilon^{\kappa\mu\nu}\left(\mathbf{J}_0\right)_\nu, \qquad (8)$$

where $\mathbf{J}_0 = 2e\int d^3k\,(2\pi)^{-3}\,(\hbar\mathbf{k}/m^*)\,\mathbf{k}\cdot\mathbf{E}\,C_k$ is the charge current in the absence of SO coupling, and summation over ν is implied. Assuming low temperatures, we need to evaluate γ_k only near the Fermi energy $E_{\rm F}$ and we defined $\gamma \equiv \gamma_{k_{\rm F}}$ [24]. If there are different species of impurity potentials, the weighted average of the corresponding transport skewnesses γ, Eq. (6), should be taken. Note that repulsive impurities generally lead to the opposite sign of γ. This can result in a partial suppression of spin Hall currents due to impurity compensation (where some acceptors are still present in an n-doped material and can localize electrons, leading to repulsive scatterers).

Next we evaluate the contribution of the side jump [21] to spin currents, where the wave function is laterally displaced during the scattering event. (This displacement does not modify the scattering angle measured at large distances, i.e., it does not affect the scattering cross section.) Side-jump currents were analyzed in detail for the anomalous Hall effect [9] and we now relate the AHE to the SHE. In the AHE, a net polarization in combination with SO interaction at impurities, leads to electrical Hall currents, even in the absence of an external magnetic field. For the SHE, electrons are unpolarized in equilibrium and we consider induced spin currents $\mathbf{j}^{\,\mu}$. Because λ is small and spin relaxation is of order λ^2 [25, 26], one can understand the $\hat{\boldsymbol{\varepsilon}}_\mu$-component of spin current as difference in particle currents of two spin species with polarizations $\pm\hat{\boldsymbol{\varepsilon}}_\mu$. For non-interacting electrons, each of these species carries the anomalous Hall current $\mathbf{J}^{\uparrow,\downarrow}_{\rm AH}$ of a system with density $n_{\rm AH} = \frac{1}{2}n$ and with spins fully aligned along the $\pm\hat{\boldsymbol{\varepsilon}}_\mu$ direction, and we can express the spin Hall current as

$$\mathbf{j}^\mu_{\rm SH} = e^{-1}\left(\mathbf{J}^{\uparrow}_{\rm AH} - \mathbf{J}^{\downarrow}_{\rm AH}\right). \qquad (9)$$

For the AHE, the side-jump contribution was found to be $\mathbf{J}^{{\rm SJ},\uparrow}_{\rm AH} = -2\,n_{\rm AH}\lambda\left(e^2/\hbar\right)\,\hat{\boldsymbol{\varepsilon}}_\mu\times\mathbf{E}$ [9]. It results from SO corrections $\delta\dot{\mathbf{r}}$ to the velocity operator during impurity scattering. Nozières and Lewiner [9] clarified that this anomalous velocity $\delta\dot{\mathbf{r}}$ comprises two equal SO contributions. The first is $\delta_1\dot{\mathbf{r}} = (i/\hbar)[H,\mathbf{r}] - \mathbf{v}_0 = (\lambda/\hbar)(\nabla V\times\boldsymbol{\sigma})$ and becomes $\delta_1\dot{\mathbf{r}} = \lambda(\boldsymbol{\sigma}\times\dot{\mathbf{k}})$ after the equation of motion, $\dot{\mathbf{k}} = -\nabla V/\hbar$, is taken into account. The second originates from the correction to the coordinate operator, the Yafet term $\delta\mathbf{r}_{\rm SO} = \lambda(\boldsymbol{\sigma}\times\mathbf{k})$ [26], and contributes as $\delta_2\dot{\mathbf{r}} = \delta_1\dot{\mathbf{r}}$. Note that $\delta_2\dot{\mathbf{r}}$ leads to a factor of 2 which is often ignored. Heuristically, we can now understand the current $\mathbf{J}^{\rm SJ}_{\rm AH}$ as follows. For scattering at an impurity with momentum transfer $\delta\mathbf{k}$, the lateral displacement it $\delta\mathbf{r} = 2\lambda(\boldsymbol{\sigma}\times\delta\mathbf{k})$. The anomalous Hall current is recovered from $\mathbf{J}^{\rm SJ}_{\rm AH} = en\,\delta\mathbf{r}/\tau$, by using that the momentum dissipated per scattering event is $\hbar\delta\mathbf{k} = -e\mathbf{E}\tau$. Using $\mathbf{J}^{\rm SJ}_{\rm AH}$ [9] and Eq. (9), we readily obtain the side jump contribution to the SHE,

$$j^\mu_{{\rm SJ},\,\kappa} = -2n\lambda\frac{e}{\hbar}\,\varepsilon^{\kappa\mu\nu}E_\nu. \qquad (10)$$

The sum $\mathbf{j}_{\rm SS} + \mathbf{j}_{\rm SJ}$ provides the total spin-Hall current.

Mathematically, one could consider a model where the electron charge is cancelled by a uniform positive background, with only small fluctuations in the potential V. In such a case, we could let τ become arbitrarily large. Although the side-jump contribution to the spin Hall conductance is independent of τ, the skew-scattering contribution, given by Eq. (8), would grow with τ. This growth would be cut off, however, when τ becomes comparable to the inverse of the SO splitting Δ due to the k^3 Dresselhaus term. If γ is small compared to $\Delta/E_{\rm F}$, as would be the case if the potential fluctuations are sufficiently small, then the skew-scattering contribution will be smaller than the intrinsic contribution by a factor of order $\gamma\,E_{\rm F}/\Delta$.

We now evaluate the skewness γ [Eq. (6)] for a screened attractive Coulomb potential. For this, we make use of the long-established theory of single electron scattering by an atom [22]. We rescale the parameters to make a connection between the atomic Hamiltonian and the effective Hamiltonian [Eq. (1)] with $V = -e^{-q_s r}\,e^2/\epsilon r$, effective mass m^*, permittivity ϵ, and screening length $1/q_s$. We match V be setting the atomic number to $Z = 1/\epsilon$. Further, to match the SO interaction, we define an "effective" speed-of-light c^* such that $\lambda = \hbar^2/4\left(m^*c^*\right)^2$. Finally, when the sign of λ differs from its vacuum value, we replace $S(\vartheta)$ by $-S(\vartheta)$ in Eq. (6) [27]. For GaAs, $\epsilon = 12.4$ and $m^* = 0.0665\,m_0$, thus $c^* \approx c/79$ and $\alpha^* Z \approx 1/21$, with fine structure constant $\alpha^* = e^2/\hbar c^*$. When evaluating $I(\vartheta)$, screening of the long-range Coulomb interaction is required, otherwise the integrals in Eq. (6) diverge, e.g., $\tau\to 0$. For exponential screening and in second order Born approximation, $I(\vartheta)$ is given by the Dalitz formula [22] (with the parameters used below and at large ϑ, it agrees well with the exact solution for the unscreened potential). We assume Thomas-Fermi screening with inverse screening length $q_s = \sqrt{3e^2n/2\epsilon E_{\rm F}}$. The numerical evaluation below shows that the transport skewness γ depends only weakly on the screening, implying that Eq. (8) is well-suited for evaluating the skew-scattering contribution. [Because of low sensitivity of γ to screening, Eq. (8) is also in agreement with the common belief that the skew-scattering contribution is proportional to τ.] When evaluating $S(\vartheta)$, we note that the main contribution comes

from large angles ϑ where the effects of screening are negligible. We thus use for $S(\vartheta)$ the exact expression for an unscreened potential [6, 22]. Note that when evaluating $S(\vartheta)$, the small parameter is $(Z\alpha^*)^2 = 4\,|\lambda|\,/(a_B^*)^2$, with effective Bohr radius $a_{\rm B}^* = \hbar^2\epsilon/m^*e^2$, so we expect $1/500$ for the order of magnitude of γ.

We now estimate γ for GaAs and for the electron density $n = 3\times10^{16}\ {\rm cm}^{-3}$ reported in Ref. 1, i.e., $E_{\rm F} = 5.3\,{\rm meV}$ and $q_s^{-1} \approx 9\,{\rm nm}$. As a test, we first evaluate the longitudinal conductivity using an impurity density $n_i = n$ and the Drude formula, $\sigma_{xx} = e^2 n\tau/m^*$ with $\tau^{-1} = n_i v_{\rm F}\int d\Omega\ I(\vartheta)\,(1-\cos\vartheta)$ and arrive at $\sigma_{xx} \approx 1.8\times10^3\ \Omega^{-1}{\rm m}^{-1}$. This is within 10% of the experimentally observed conductivity at low voltages; a surprisingly good agreement, given that the rather small value $k_{\rm F}\ell \approx 2$ restricts the accuracy of the Boltzmann approach. Next we evaluate Eq. (6) and find $\gamma \approx 1/900$. This value is rather stable and changes by less than 30% when q_s or $E_{\rm F}$ increase or decrease by a factor of two.

Next, we estimate the spin Hall currents. The measurements were performed at electrical fields $E \approx 20\,{\rm mV}\,\mu{\rm m}^{-1}$ where the conductivity increased to $\sigma_{xx} \approx 3\times10^3\ \Omega^{-1}{\rm m}^{-1}$ due to electron heating. We assume that γ is not very sensitive to these heating effects and we still use Eq. (8) but with the increased conductivity. For an electrical field $\mathbf{E} = \hat{\mathbf{x}}\,E_x$, we find both contributions to the spin Hall conductivity $\sigma^{\rm SH} \equiv -j_y^z/E_x$, namely $\sigma_{\rm SS}^{\rm SH} = -(\gamma/2e)\sigma_{xx} \approx 1.7\,\Omega^{-1}{\rm m}^{-1}/|e|$ and $\sigma_{\rm SJ}^{\rm SH} = 2n\lambda e/\hbar \approx -0.8\Omega^{-1}{\rm m}^{-1}/|e|$. In total, we arrive at the extrinsic spin Hall conductivity $\sigma_{\rm th.}^{\rm SH} \approx 0.9\,\Omega^{-1}{\rm m}^{-1}/|e|$ [28]. The magnitude is within the error bars of the experimental value of $\left|\sigma_{\rm exp.}^{\rm SH}\right| \approx 0.5\ \Omega^{-1}{\rm m}^{-1}/|e|$ found from spin accumulation near the free edges of the specimen [1, 29].

Bernevig and Zhang calculated intrinsic spin currents due to k^3-Dresselhaus interaction [16]. In contrast to the case of spin-orbit interactions linear in $\mathbf{k}$, where vertex corrections lead to a cancellation of the spin current [12, 30, 31], for the k^3 interaction this is not true; e.g., for s-wave scatterers the vertex corrections vanish identically [32]. However, in the dirty limit $\tau\Delta/\hbar \sim 10^{-2}$, where Δ is the SO splitting Δ at the Fermi level and for experimental parameters of Ref. 1, intrinsic spin currents were found to be small, only $\sigma_{\rm D} \approx 0.02\,\Omega^{-1}{\rm m}^{-1}/|e|$ [16].

In conclusion, we solved the kinetic equation including skew-scattering at impurities. We derived the contributions to the extrinsic spin Hall effect and found reasonable agreement with experimental data. We acknowledge discussions with D.D. Awschalom, B.A. Bernevig, E. Demler, Y.K. Kato, D. Loss, A.H. MacDonald, E.G. Mishchenko, A. Stern, R. Winkler, and S.-C. Zhang. This work was supported in part by NSF grants DMR-02-33773, PHY-01-17795, the Harvard Center for Nanoscale Systems, and DARPA.

[1] Y.K. Kato, R.C. Myers, A.C. Gossard, and D.D. Awschalom, Science **306**, 1910 (2004).

[2] J. Wunderlich, B. Kaestner, J. Sinova, and T. Jungwirth, Phys. Rev. Lett. **94**, 047204 (2005).

[3] M.I. Dyakonov and V.I. Perel, Phys. Lett. **35A**, 459 (1971).

[4] J.E. Hirsch, Phys. Rev. Lett. **83**, 1834 (1999).

[5] S. Zhang, Phys. Rev. Lett. **85**, 393 (2000).

[6] N.F. Mott and H.S.W. Massey, *The Theory of Atomic Collisions* (Oxford University Press, 1965).

[7] S. Murakami, N. Nagaosa, and S.-C. Zhang, Science **301**, 1348 (2003).

[8] J. Sinova, D. Culcer, Q. Niu, N.A. Sinitsyn, T. Jungwirth, and A.H. MacDonald, Phys. Rev. Lett. **92**, 126603 (2004).

[9] P. Nozières and C Lewiner, J. Phys. (Paris) **34**, 901 (1973), their SO coupling constant is $\lambda_{\rm NL} = 2\lambda/\hbar$.

[10] A. Crépieux and P. Bruno, Phys. Rev. B **64**, 014416 (2001).

[11] See, e.g., A.A. Burkov, A.S. Núñez, and A.H. MacDonald, Phys. Rev. B **70**, 155308 (2004); S.I. Erlingsson, J. Schliemann, and D. Loss, *ibid.* **71**, 035319 (2005); O.V. Dimitrova, cond-mat/0405339v2.

[12] E.G. Mishchenko, A.V. Shytov, and B.I. Halperin, Phys. Rev. Lett. **93**, 226602 (2004).

[13] In Ref. 1, a model with spin diffusion and spin relaxation is used to relate observed spin accumulation at the boundaries to a bulk spin Hall current.

[14] E.I. Rashba, Phys. Rev. B **68**, 241315 (2003).

[15] G.Dresselhaus, Phys. Rev. **100**, 580 (1955).

[16] B.A. Bernevig and S.-C. Zhang, cond-mat/0412550.

[17] G. Usaj and C.A. Balseiro, cond-mat/0405065v2.

[18] B.K. Nikolic, S. Souma, L.P. Zarbo, and J. Sinova, cond-mat/0412595.

[19] Y.K. Kato and D.D. Awschalom (private communication).

[20] R. Winkler, *Spin-Orbit Coupling Effects in Two-Dimensional Electron and Hole System* (Springer, 2003).

[21] L. Berger, Phys. Rev. B **2**, 4559 (1970).

[22] J.W. Motz, H. Olsen, and H.W. Koch, Rev. Mod. Phys. **36**, 881 (1964), Sec. VI and Eqs. (1A-107) and (1A-403).

[23] H.C. Huang, O. Voskoboynikov, and C.P. Lee, Phys. Rev. B **67**, 195337 (2003).

[24] The skew-scattering contribution for a 2D system is obtained by replacing $\frac{1}{2}\gamma \to \gamma^{\rm 2D}$ in Eqs. (7)–(8), where $\gamma^{\rm 2D}$ is given by Eq. (6) after replacing $\int d\Omega \to \int_0^\pi d\vartheta$. For example, using the same parameters as in the text, we obtain $\gamma^{\rm 2D} \approx 1/1300$. However, in 2D, both transport and calculation of cross sections [23] are complicated by the presence of intrinsic k-linear terms (Rashba and Dresselhaus) which are difficult to avoid.

[25] R.J. Elliott, Phys. Rev. **96** (1954).

[26] Y. Yafet, Solid State Physics **14**, 1 (1963), eds. F. Seitz and D. Turnbull (Academic, NY). In modern terms, $\delta\dot{\mathbf{r}}_{\rm SO}$ is related to the Berry curvature.

[27] We do not renormalize higher-order or spin-independent relativistic terms; their effect should be small and is disregarded.

[28] From σ_{xx} we extract a rather small value $k_{\rm F}\ell \approx 4$, i.e., the accuracy of the Boltzmann approach is restricted.

[29] Qualitatively, our model also agrees with the main observations. First, because Eq. (1) is based on s- and p-band interaction, our model is isotropic, consistent with the observation of an isotropic spin Hall effect. Second, it is compatible with the interpretation of the shifted Kerr rotation data due to strain-induced spin-orbit fields, see Fig. 4 of Ref. 1.
[30] J.I. Inoue, G.E.W. Bauer, and L.W. Molenkamp, Phys. Rev. B **70**, 041303 (2004).
[31] O. Chalaev and D. Loss, cond-mat/0407342v2.
[32] E.G. Mishchenko (private communication); S.-C. Zhang (private communication).

Appendix A: ANGULAR INTEGRALS

For completeness, we now show how the angular integrals in Eqs. (4) and (5) can be evaluated. Without loss of generality, we choose the coordinate system $\mathbf{k} = (0,\, 0,\, k)$ and parameterize $\mathbf{k}' = k\,(\cos\varphi \sin\vartheta,\, \sin\varphi \sin\vartheta,\, \cos\vartheta)$ since $k' = k$. We set $\mathbf{a} = (\mathbf{E}\, C_k + \mathbf{P} \times \mathbf{E}\, D_k)$ and Eq. (4) is obtained from

$$\begin{aligned}
&\int d\Omega(\mathbf{k}')\, I\,(\vartheta)\; (\mathbf{k} - \mathbf{k}') \cdot \mathbf{a} \\
&= \int d\Omega\, I\,(\vartheta)\; \big[k\, a_z\,(1 - \cos\vartheta) - k\, a_x \cos\varphi \sin\vartheta \\
&\qquad - k\, a_y \sin\varphi \sin\vartheta\big] \\
&= \mathbf{k} \cdot \mathbf{a} \int d\Omega\, I\,(\vartheta)\; (1 - \cos\vartheta)\,, \qquad \text{(A1)}
\end{aligned}$$

where we used in the last line that integration over $d\Omega$ removes the terms in $\sin\varphi$ and $\cos\varphi$ and that $k\, a_z = \mathbf{k} \cdot \mathbf{a}$. Next, we note that $\mathbf{n} = \mathbf{k}' \times \mathbf{k} / |\mathbf{k}' \times \mathbf{k}| = (\sin\phi,\, -\cos\phi,\, 0)$ and insert into the left hand side of Eq. (5),

$$\begin{aligned}
&\int d\Omega(\mathbf{k}')\, I\,(\vartheta)\, S\,(\vartheta)\, (\boldsymbol{\sigma} \cdot \mathbf{n})\, (\mathbf{k} \cdot \mathbf{E} - \mathbf{k}' \cdot \mathbf{E})\, C_k \\
&= \int d\Omega\,(\mathbf{k}')\;\, I\,(\vartheta)\, S(\vartheta)\;\, (\sigma_x \sin\varphi - \sigma_y \cos\varphi) \\
&\qquad \times \big[k\, E_z\,(1 - \cos\vartheta) - k\, E_x \cos\varphi \sin\vartheta \\
&\qquad\quad - k\, E_y \sin\varphi \sin\vartheta\big] C_k \\
&= -\frac{1}{2}\,(k\, \sigma_x E_y - k\, \sigma_y E_x)\, C_k \int d\Omega\,(\mathbf{k}')\;\, I\,(\vartheta)\, S(\vartheta)\;\, \sin\vartheta, \\
&\qquad\qquad\qquad\qquad\qquad\qquad\qquad\qquad\qquad\qquad \text{(A2)}
\end{aligned}$$

using that also terms in $\sin\varphi\cos\varphi$ vanish after integration and that $\int d\varphi\, \cos^2\varphi = \int d\varphi\, \sin^2\varphi = \frac{1}{2}\int d\varphi$. From $k\, \sigma_x E_y - k\, \sigma_y E_x = \mathbf{k} \cdot (\boldsymbol{\sigma} \times \mathbf{E})$, we recover the r.h.s of Eq. (5).